

1-1-1991

# Frustration and microstructure : an example in magnetostriction

Richard D. James  
*Carnegie Mellon University*

David Kinderlehrer

Follow this and additional works at: <http://repository.cmu.edu/math>

---

## Recommended Citation

James, Richard D. and Kinderlehrer, David, "Frustration and microstructure : an example in magnetostriction" (1991). *Department of Mathematical Sciences*. Paper 309.  
<http://repository.cmu.edu/math/309>

This Technical Report is brought to you for free and open access by the Mellon College of Science at Research Showcase. It has been accepted for inclusion in Department of Mathematical Sciences by an authorized administrator of Research Showcase. For more information, please contact [research-showcase@andrew.cmu.edu](mailto:research-showcase@andrew.cmu.edu).

**NOTICE WARNING CONCERNING COPYRIGHT RESTRICTIONS:**  
The copyright law of the United States (title 17, U.S. Code) governs the making of photocopies or other reproductions of copyrighted material. Any copying of this document without permission of its author may be prohibited by law.



NAMT

91-012

Frustration and Microstructure:  
An Example in Magnetostriction

Richard D. James  
Department of Aerospace Engineering and Mechanics  
University of Minnesota  
Minneapolis, MN 55455

and

David Kinderlehrer  
Department of Mathematics  
Carnegie Mellon University  
Pittsburgh, PA 15213

Research Report No. 91-NA-012

November 1991

**Center for  
Nonlinear Analysis**

**Department of Mathematics  
Carnegie Mellon University  
Pittsburgh, PA 15213-3890**

Sponsored by  
U.S. Army Research Office  
Research Triangle Park  
North Carolina 27709

National Science Foundation  
1800 G Street, N.W.  
Washington, DC 20550

University Libraries  
Carnegie Mellon University  
Pittsburgh, PA 15213-3890

# Frustration and Microstructure: An Example in Magnetostriction

Richard D. James  
Department of Aerospace Engineering and Mechanics  
University of Minnesota  
Minneapolis, MN 55455

and

David Kinderlehrer  
Department of Mathematics  
Carnegie Mellon University  
Pittsburgh, PA 15213

Research Report No. 91-NA-012

November 1991

University Libraries  
Carnegie Mellon University  
Pittsburgh, PA 15213-3890



## Frustration and Microstructure: An Example in Magnetostriction

Richard D. James and David Kinderlehrer

**Abstract** Microstructural properties of materials, especially crystalline solids, are implicated in many of their properties. Vice versa, there are macroscopic environments which limit microstructural configurations. Certain iron/rare earth alloys, eg,  $TbDyFe_2$ , display both a huge magnetostriction and frustration, i.e., minimum energy not achieved, in which microstructure plays an important, if puzzling, role. We discuss this example in the framework of continuum thermoelasticity theory, where symmetry demands energy densities which are highly degenerate. This leads to novel analytical and computational issues, many of which we have been unable to resolve.

1.	Introduction.....	1
2.	Energy of magnetostriction.....	3
3.	A variational principle.....	6
4.	Description of the equilibrium microstructure.....	13
5.	Magnetic fine structure.....	17
	References.....	20

### 1. Introduction

Crystals are idealized as materials with a high degree of configurational order<sup>1</sup>. As a consequence, the continuum energy densities ascribed to them are invariant under discrete groups and have multiple potential wells. Such densities are not lower semicontinuous. The infimum of energy may be obtained only in some generalized sense, while a minimizing sequence may develop successively finer oscillations. The limit deformation alone need not be sufficient to characterize many of the properties of the limit configuration. Martensitic materials, in particular, exhibit fine structure in the form of fine twinned microstructure, often appearing as layers or layers within layers.

A remarkable feature of ferromagnetic materials is that the single domain state is generally unstable. This contrasts with martensite, where the single variant configuration is stable for arbitrarily large samples. In the blue phase of cholesteric liquid crystals, the failure of stability of the uniform state relative to an array of defects is termed *frustration*, cf. Sethna [62]. Our

---

<sup>1</sup> Research group *Transitions and Defects in Ordered Materials*, funded by the NSF and the AFOSR (DMS 87-18881) and by the ARO (DAAL 03 88 K 0010).

calculations here could be interpreted as one possible interpretation of this phenomenon at a macroscopic scale. The frustration in our system arises from the competition of an anisotropy energy which demands constant magnetization strength and direction with an induced field energy which prefers to tend to zero. A consequence of this is to promote development of a fine scale structure which seeks to compromise the constraint of constant magnetization strength. A different mechanism is given by Sethna for the blue phase.

Certain iron/rare earth alloys display both frustration and a huge magnetostriction. There are cubic Laves phase  $RFe_2$  ( $R =$  rare earth) compounds, for example, where magnetically induced strains "overwhelm the conventional thermal expansion of the material", Clark [16].  $TbDyFe_2$  (terfenol) solidifies from the melt with a textured microstructure which plays an important, if puzzling, role in its magnetostrictive properties. Our objective in this note is to describe briefly a theory of magnetoelastic interactions based on the micromagnetics of W. F. Brown, Jr. [10,11,12] and the symmetry considerations introduced by Ericksen [23-31]. It has some similarities with Toupin's theory of the elastic dielectric [70]. We shall then illustrate how the equilibrium microstructure of  $TbDyFe_2$  is consistent with this theory. Our information about the properties of  $TbDyFe_2$  comes primarily from Lord [53].

For relatively rigid materials one may assume the free energy to depend on magnetization alone, [39,40,51]. The theory in this case gives good qualitative agreement with experiment, explaining why cubic magnets have a few large domains and why uniaxial ones have a fine structure. Domain refinement at the boundary is also predicted when the normal to the boundary has a suitable orientation with relative to the crystal axes, in agreement with observations.

The analysis introduced to study the micromagnetic theory is based on the study of minimizing sequences, or devices used to summarize their oscillatory behavior. This gives a reasonable description of microscopic aspects of domain structure and macroscopic state functions. The particular averaging device used by us is the Young measure, Young [72], and first introduced in partial differential equations by Tartar [68,69]. The Young measure is particularly useful for predicting where in the body fine structure will occur. We refer to Ball [3], Ball and James [4,5], Chipot [14], Chipot and Kinderlehrer [13], Collins and Luskin [17,18,19], Collins, Kinderlehrer, and Luskin [20], Firooze and Kohn [32], Fonseca [33,34,35], James [36,37], James and Kinderlehrer [38], Kinderlehrer [43], Kohn [48,49], Matos [57], Pedregal [58,59], Sverak [64-67], and Zhang [73,74].

In addition to Brown's work, general references to the theory of ferromagnetism and ferromagnetic domain structure include Clark [16], Craik and Tebble [21], Kléman [47], Landau and Lifshitz [50], Landau, Lifshitz and Piatevskii [51], and Lifshitz [52]. Recent mathematical analysis includes Anzellotti, Baldo, and Visintin [1], Brandon and Rogers [9], Rogers [60,61],



and Visintin [71]. Computational aspects of micromagnetics have been studied by Luskin and Ma [54] and Ma [55].

## 2. Energy of magnetostriction

Equilibrium configurations of the system are interpreted as stationary points of a variational principle which consists of the sum of a stored energy and the induced magnetic field energy. In this section we describe the energy of a configuration and in §3 we discuss a variational principle. The stored energy density of the material will depend on the deformation gradient  $F \in \mathbb{M}$ ,  $3 \times 3$  matrices, magnetization (per unit mass)  $m \in \mathbb{R}^3$ , and temperature  $\theta \in \mathbb{R}$ . We suppose it given by a nonnegative function

$$W(F, m, \theta) \quad F \in D, m \in \mathbb{R}^3, \theta \in \mathbb{R}, \quad (2.1)$$

where  $D \subset \mathbb{M}$  is a suitable domain of matrices with positive determinant. It is subject to the condition of frame indifference

$$W(QF, mQ^T, \theta) = W(F, m, \theta), \quad Q \in \text{SO}(3), \quad (2.2)$$

and  $F, m, \theta$  as in (2.1). We also impose a condition of material symmetry which is derived from a Cauchy-Born rule applied to the symmetry imputed to the underlying crystal lattice. This is explained in [41] and relies on the ideas set forth by Ericksen [24]. This symmetry is that

$$W(FP, m, \theta) = W(F, m, \theta), \quad P \in \mathbb{P}, \quad (2.3)$$

where  $\mathbb{P}$  is a crystallographic point group. We are hesitant to impose full magnetic symmetry including invariance under time reversals for reasons explained in [41].

In the spatial configuration, Maxwell's equations hold. Let  $y$  denote the spatial variable and  $B, H$ , and  $M$  denote the magnetic induction, the magnetic field, and the magnetization (dipole moment per unit volume), respectively. Then, for an appropriate choice of units,

$$\begin{aligned} B &= H + M, \\ \text{div}_y B &= 0 \quad \text{and} \quad \text{curl}_y H = 0 \quad \text{in } \mathbb{R}^3. \end{aligned} \quad (2.4)$$

Introducing  $U(y)$  for which  $H = -\nabla_y U$ , we obtain that (2.4) is equivalent to

$$\text{div}_y (-\nabla_y U + M) = 0 \quad \text{in } \mathbb{R}^3. \quad (2.5)$$

The field energy density is given by

$$\frac{1}{2} |H|^2 = \frac{1}{2} |\nabla_y U|^2.$$

The material is assumed magnetically saturated, leading to the constraint

$$|\frac{M}{\rho}| = f(\theta) \quad \text{in the body,} \quad (2.6)$$

where  $\rho$  is the density, cf. Brown [11], James and Müller [42], Landau and Lifschitz [50].

Assume now that initially the material occupies a reference configuration  $\Omega \subset \mathbb{R}^3$  and has constant density  $\rho_0$ . As discussed below,  $\Omega$  is interpreted as an undistorted single crystal above the Curie temperature. By an abuse of notation, let  $y(x)$  denote the deformation of  $\Omega$  to  $y(\Omega)$ , assumed for the purposes of discussion to be 1:1. Since  $\rho(x) = \rho_0 / \det \nabla y(x)$ , the magnetization per unit mass previously introduced,

$$m = \frac{1}{\rho_0} \det \nabla y M,$$

so the constraint (2.6) assumes the form

$$|m| = f(\theta).$$

For our purposes it suffices to assume that  $\rho_0 = 1$ ,  $m = m(x)$  and

$$\begin{aligned} m &= 0 && \text{if } \theta > \theta_0 \text{ and} \\ |m| &= 1 && \text{in } \Omega \text{ at } \theta < \theta_0, \end{aligned} \quad (2.7)$$

where  $\theta_0$  is the Curie point (associated with the onset of magnetization) and  $\theta$  is fixed for our purposes.

In this fashion we may write the virtual energy of the configuration  $y = y(x)$ ,  $m = m(x)$  in the mixed reference/spatial form

$$E(y,m) = \int_{\Omega} W(\nabla y, m, \theta) dx + \frac{1}{2} \int_{\mathbb{R}^3} |\nabla_y U|^2 dy \quad (2.8)$$

subject to the constraints, cf. (2.4) and (2.7),

$$\operatorname{div}_y (-\nabla_y U + \frac{1}{\det \nabla y} m) = 0 \quad \text{in } \mathbb{R}^3. \quad (2.9)$$

$$|m| = 1 \quad \text{in } y(\Omega).$$

From (2.9), we may also write the energy in the form

$$E(y,m) = \int_{\Omega} W(\nabla y, m, \theta) dx + \frac{1}{2} \int_{\Omega} \frac{1}{\det \nabla y} m \cdot \nabla y U dy . \quad (2.10)$$

To express this in terms of reference variables alone, introduce  $u(x) = U(y(x))$ , so  $\nabla u(x) = \nabla_y U(y(x))F(x)$ ,  $F(x) = \nabla y(x)$ . With  $C = F^T F$ , the constraint equation (2.9) becomes

$$\operatorname{div}(-\nabla u C^{-1} \det F + m F^{-T}) = 0 \quad \text{in } \mathbb{R}^3, \quad (2.11)$$

and the saturation condition is simply

$$|m| = 1 \quad \text{in } \Omega. \quad (2.12)$$

The virtual energy of  $y = y(x)$ ,  $m = m(x)$  in reference form is

$$E(y,m) = \int_{\Omega} W(\nabla y, m, \theta) dx + \frac{1}{2} \int_{\mathbb{R}^3} \nabla u C^{-1} \cdot \nabla u \det F dx, \quad (2.13)$$

subject to (2.11) and (2.12). Analogous to (2.10), we may also write (2.13) as

$$E(y,m) = \int_{\Omega} W(\nabla y, m, \theta) dx + \frac{1}{2} \int_{\mathbb{R}^3} \nabla u \cdot m F^{-T} dx. \quad (2.14)$$

We wish to note here in a parenthetical fashion that in (2.11), (2.13) and (2.14) we have conveniently ignored the behavior of  $y$  outside of the region  $\Omega$  occupied by the material. Without entering into a complete discussion of this issue, let us consider the most naive point of view. Suppose that  $y$  is a 1:1 deformation of  $\Omega$  defined on all of  $\mathbb{R}^3$  and that  $y'(x) = y(\eta(x))$  where  $\eta(x) = x$  in  $\Omega$ . The potential  $U(y)$  is then independent of the choice of mapping  $y$  or  $y'$  and so is the expression (2.10). Thus the energy of a configuration does not depend on the particular extension of  $y(x)$  if  $y|_{\Omega}$  is 1:1.

Moreover, as we shall illustrate shortly, the infimum of  $E(y,m)$  depends only on  $y|_{\Omega}$  in situations of interest.

The symmetry condition (2.3) induces a potential well structure on  $W$ . Our schema for understanding this well structure begins by choosing for  $\mathbb{P}$  the symmetry group of a putative high temperature non-magnetic parent phase of the material. For example, in the case we shall consider here,  $\mathbb{P}$  is the cubic group of order 24: relative to a cubic basis, these are the proper orthogonal matrices of the form  $P = (p_{ij})$ ,  $p_{ij} = \pm 1$  or 0. This is the appropriate assumption for  $\text{TbDyFe}_2$ . For  $\theta < \theta_0$ , we assume there exists a pair  $(U_1, m_1)$  with  $|m_1| = 1$  and  $U_1 = U_1^T$  positive definite satisfying

$$W(U_1, m_1, \theta) \leq W(F, m, \theta) \quad \text{for } F \in D, |m| = 1. \quad (2.15)$$

Generally,  $U_1$  and  $m_1$  depend on temperature. The conditions (2.7) and (2.8) imply the existence of other minima by (2.9). We shall assume that *the full set of minima is determined by the orbits of  $(U_1, m_1)$  under these actions*. Thus

$$\begin{aligned} \inf W = W(RU_1H, m_1R^T) < W(F, m) \quad \text{for } R \in \text{SO}(3), H \in \mathbb{P} \\ \text{and } F \in \mathbb{M}, |m| = 1, \text{ with } (F, m) \neq (RU_1H, m_1R^T). \end{aligned} \quad (2.16)$$

The potential wells may be described as

$$\begin{aligned} (RU_1, m_1R^T), \quad R \in \text{SO}(3), \\ (RU_2, m_2R^T), \quad R \in \text{SO}(3), \\ \cdot \\ \cdot \\ \cdot \\ (RU_n, m_nR^T), \quad R \in \text{SO}(3), \end{aligned} \quad (2.17)$$

where

$$\{(U_1, m_1), (U_2, m_2), \dots, (U_n, m_n)\} = \{(QU_1Q^T, m_1Q^T): Q \in \mathbb{P}\}.$$

An orbit of the form  $(RU_i, m_iR^T)$ ,  $R \in \text{SO}(3)$ , will be called a *variant*.

### 3. A variational principle

We would like to investigate variational principles compatible with minimizing the functional (2.8) or (2.13). A first requirement is that a variational principle be capable of delivering the possible minimum energy configurations determined by the well structure described in the preceding section. We formulate here a requirement for this which is a slight modification of our treatment of the rigid ferromagnet [40]. In this section we suppress the dependence of various quantities on temperature  $\theta$ .

**THEOREM 3.1** *Assume that there exists a pair  $(F_0, m_0)$  with  $\det F_0 > 0$  and  $|m_0| = 1$  such that*

$$W(F_0, m_0) = W(F_0, -m_0) = \min W.$$

*Then there is a sequence  $(y^k, m^k)$  such that*

$$y^k: \mathbb{R}^3 \rightarrow \mathbb{R}^3 \text{ is 1:1 and } m^k: \Omega \rightarrow \mathbb{S}^2$$

with  $\det \nabla y^k = \det F_0$  such that

$$\lim_{k \rightarrow \infty} E(y^k, m^k) = \min W | \Omega |. \quad (3.1)$$

PROOF. In fact, we choose  $y^k(x) = y_0(x) \equiv F_0 x$  for all  $k$ . Let  $n \in \mathbb{S}^2$  satisfy  $n \cdot m_0 F_0^{-T} = 0$ . Set

$$\vartheta(t) = \begin{cases} -1 & 0 \leq t < \frac{1}{2} \\ +1 & \frac{1}{2} \leq t < 1 \end{cases},$$

and extend  $\vartheta$  to be periodic of period 1 on  $\mathbb{R}$ . Define

$$\begin{aligned} f^k(x) &= \vartheta(kn \cdot x) m_0 F_0^{-T}, \quad k = 1, 2, 3, \dots \text{ and} \\ m^k(x) F_0^{-T} &= \chi_{\Omega} f^k(x) = \vartheta(kn \cdot x) \chi_{\Omega} m_0 F_0^{-T}, \quad k = 1, 2, 3, \dots \end{aligned}$$

Note that by the choice of  $\vartheta$  and  $n$ ,

$$f^k \rightarrow 0 \text{ in } L^{\infty}(\mathbb{R}^3; \mathbb{R}^3) \text{ weak* and} \quad (3.2)$$

$$\operatorname{div} f^k = 0 \text{ in } H_{loc}^{-1}(\mathbb{R}^3). \quad (3.3)$$

Now let us note the lemma below, cf. Rogers [61] or [41].

LEMMA 3.2 *If  $(f^k)$  satisfy (3.2) and (3.3), then*

$$\operatorname{div} \chi_{\Omega} f^k \rightarrow 0 \text{ in } H^{-1}(\mathbb{R}^3).$$

For the proof of the lemma, we refer to [41]. To continue the proof of the theorem, note that  $C_0^{-1} \det F_0$  is positive definite, hence there is a solution

$$u^k \in V: \operatorname{div} (-\nabla u^k C_0^{-1} \det F_0 + m^k F_0^{-T}) = 0 \text{ in } H^{-1}, \text{ where}$$

$$V = \{ v \in H_{loc}^1(\mathbb{R}^3): \nabla v \in L^2(\mathbb{R}^3) \},$$

which satisfies

$$\| \nabla u^k \|_{L^2(\mathbb{R}^3)} \leq \operatorname{const} \| m^k F_0^{-T} \|_{L^2(\mathbb{R}^3)} \leq M.$$

Finally,

$$\begin{aligned}
\min W|\Omega| \leq E(y^k, m^k) &= \min W|\Omega| + \frac{1}{2} \int_{\mathbb{R}^3} \nabla u^k \cdot m^k F_o^{-T} \, dx \\
&\leq \min W|\Omega| + \frac{1}{2} \|\nabla u^k\|_{L^2(\mathbb{R}^3)} \|\operatorname{div} m^k F_o^{-T}\|_{H^{-1}(\mathbb{R}^3)} \\
&= \min W|\Omega| + \frac{1}{2} \|\nabla u^k\|_{L^2(\mathbb{R}^3)} \|\operatorname{div} f^k \chi_\Omega\|_{H^{-1}(\mathbb{R}^3)}.
\end{aligned}$$

Applying the lemma to the last term,

$$\lim_{k \rightarrow \infty} E(y^k, m^k) = \min W|\Omega|. \quad \text{QED}$$

Since the right hand side of (3.1) is the minimum possible value of  $E(y, m)$ , the theorem serves us as a criterion in several ways. Any variational principle must recover the infimum of the functional. Also, later on, we can use THEOREM 3.1 to check that a given configuration is of minimum energy.

Rather than survey all the possibilities for minimum principles, let us adopt a point of view convenient for analytical purposes by choosing a reference formulation. In finite elasticity we do not generally require that the admissible deformations be 1:1, although there are occasions where this is feasible to prove (Ball [2], Ciarlet and Necas [15], Fonseca [35]), but we do ask that local orientation be preserved. So one generally imposes the condition that either  $\det \nabla y > 0$  for an admissible deformation  $y$  or that

$$W(A, m) = \infty \text{ when } \det A \leq 0.$$

In the present situation, we are also asked to resolve the constraint equation (2.11), which we interpret to mean, cf. LEMMA 3.2,

$$u \in V: \operatorname{div} (-\nabla u C^{-1} \det F + m F^{-T}) = 0 \text{ in } H^{-1}(\mathbb{R}^3), \text{ where} \quad (3.4)$$

$$V = \left\{ v \in H_{loc}^1(\mathbb{R}^3): \nabla v \in L^2(\mathbb{R}^3), \int_{\{|x| \leq 1\}} v \, dx = 0 \right\},$$

when  $F = \nabla y$ , with  $y$  an admissible variation. For this it is convenient to assure that the matrix  $C^{-1} \det F$  is positive definite and that the term  $\operatorname{div} (m^k F^{-T})$  is in  $H^{-1}$ . Our technique is to adopt a van der Waals condition and to assume in addition that  $y$  has bounded derivatives. This will permit us to infer, for example, that

$$(i) \quad \text{if } u \in V \text{ satisfies (3.4), then } \|u\|_V \leq \text{const.} \quad \text{and} \quad (3.5)$$

$$(ii) \quad \text{if } \frac{1}{2} \int_{\mathbf{R}^3} \nabla u^k (C^k)^{-1} \cdot \nabla u^k \det F^k dx \rightarrow 0, \text{ then } u^k \rightarrow 0 \text{ in } V \quad (3.6)$$

As we have been suggesting, there are many ways to achieve these conditions, but we should like to consider one which has been under discussion for some time, although it may not have appeared explicitly in the literature, and is common in the study of duality theory. Recently it has been taken up by Ball and James [5] and Kinderlehrer and Pedregal [44,45].

We shall assume that there is a subset  $D \subset \mathbb{M}$  such that

$$W(A,m) \begin{cases} < \infty & A \in D \\ = +\infty & A \notin D \end{cases} \quad (3.7)$$

About  $D$  we impose these requirements:

$$\Sigma = \{A: W(A,m) = \inf W\} \subset D, \quad (3.8)$$

$$D \subset \{A: \det A \geq \delta\}, \text{ where } \delta > 0 \text{ is given,} \quad (3.9)$$

$$D\mathbb{P} \subset D, \text{ i.e., } D \text{ is invariant under the symmetry group } \mathbb{P}, \text{ and} \quad (3.10)$$

$$D \text{ is the closure of a bounded open convex set.} \quad (3.11)$$

Let us assume that the symmetry group  $\mathbb{P} \subset \text{SO}(3)$ . Suppose that any  $A$  in the potential wells defined by (2.17) satisfies

$$|\text{tr}(A^T A - 1)| = ||A|^2 - 3| \leq r \quad (3.12)$$

with  $r$  so small that (3.12) ensures that  $\det F \geq \delta > 0$ . We let the domain  $D$  where  $W(F,m)$  is defined as a function of  $F$  be determined by (3.12). It is invariant under the action of  $\mathbb{P}$  and is convex. Thus all the properties (3.8) - (3.11) are satisfied. (3.9) and (3.11) imply that the constraint equation is well behaved, (3.5) and (3.6). In [5] it is shown how to obtain a  $D$  satisfying (3.8) - (3.10) with a general well structure.

A first advantage of (3.12) is that it permits us to understand the relaxation of the energy functional. In general, let  $K$  be the closure of a bounded open convex set. Given  $\psi \in C(K)$ , set

$$\hat{\psi}(A) = \begin{cases} \psi(A) & A \in K \\ \infty & \text{otherwise} \end{cases} \quad (3.13)$$

Let

$$\hat{\Psi}^\#(A) = \inf_{H_0^{1,\infty}(\Omega;\mathbb{R}^3)} \frac{1}{|\Omega|} \int_{\Omega} \hat{\Psi}(A+\nabla\zeta) dx, \quad A \in M \quad (3.14)$$

Then  $\hat{\Psi}^\#(A) = +\infty$  for  $A \notin K$ ,

$\hat{\Psi}^\#(A)$  is quasiconvex, and

$$\Psi^\#(v) = \int_{\Omega} \hat{\Psi}^\#(\nabla v) dx, \quad v \in H_0^{1,\infty}(\Omega;\mathbb{R}^3),$$

is sequentially weak\* lower-semicontinuous [44]. In addition a relaxation result is valid. Suppose that

$$y_0 \in H^{1,\infty}(\Omega;\mathbb{R}^3): \int_{\Omega} \hat{\Psi}(\nabla y_0) dx < +\infty.$$

Then

$$\inf_A \int_{\Omega} \hat{\Psi}(\nabla y) dx = \inf_A \int_{\Omega} \hat{\Psi}^\#(\nabla y) dx, \quad (3.15)$$

$$A = \{y \in H^{1,\infty}(\Omega;\mathbb{R}^3): y = y_0 \text{ on } \partial\Omega\}.$$

We have not at present identified the relaxation of a functional of the form

$$\int_{\Omega} \Psi(\nabla y, m) dx, \quad y \in H^{1,\infty}(\Omega;\mathbb{R}^3), \quad m \in L^\infty(\Omega;\mathbb{S}^2)$$

nor of

$$\int_{\Omega} \hat{\Psi}(\nabla y, m) dx, \quad y \in H^{1,\infty}(\Omega;\mathbb{R}^3), \quad m \in L^\infty(\Omega;\mathbb{S}^2).$$

However, it is possible to give the partial result that, for  $m \in L^\infty(\Omega;\mathbb{S}^2)$  fixed,

$$\inf_A \int_{\Omega} \hat{\Psi}(\nabla y, m) dx = \inf_A \int_{\Omega} \hat{\Psi}^\#(\nabla y, m) dx, \quad (3.16)$$

$$A = \{y \in H^{1,\infty}(\Omega;\mathbb{R}^3): y = y_0 \text{ on } \partial\Omega\},$$



where for each fixed unit vector  $\mu$ ,

$$\hat{\psi}^\#(A, \mu) = \inf_{H_o^{1,\infty}(\Omega; \mathbb{R}^3)} \frac{1}{|\Omega|} \int_{\Omega} \hat{\psi}(A + \nabla \zeta, \mu) dx, \quad A \in \mathbb{M}. \quad (3.17)$$

This can be proved by modification of a known method, Marcellini [56], Dacorogna [22].

We next wish to investigate the limit configurations available to the energy  $E(y, m)$ . These are given by the possible minimizing sequences in terms of the Young measures they define. Suppose that  $(y^k, m^k)$ ,  $\nabla y^k = F^k$ , is a minimizing sequence with the property

$$(y^k, m^k) \rightarrow (y, \bar{m}) \quad \text{in } H^{1,\infty}(\mathbb{R}^3; \mathbb{R}^3) \times L^\infty(\Omega; \mathbb{S}^2) \text{ weak}^*. \quad (3.18)$$

Then there is a family  $\nu = (\nu_x)_{x \in \mathbb{R}^3}$  of probability measures such that whenever  $\psi \in C(\mathbb{M} \times \mathbb{S}^2)$ ,

$$\psi(F^k, m^k) \rightarrow \bar{\psi} \quad \text{in } L^\infty(\mathbb{M} \times \mathbb{S}^2; \mathbb{R}) \text{ weak}^*, \text{ where}$$

$$\bar{\psi}(x) = \int_{\mathbb{M} \times \mathbb{S}^2} \psi(A, \mu) d\nu_x(A, \mu) \quad \text{in } \mathbb{R}^3 \text{ a.e.}$$

Let us isolate several basic features of the variational principle in this context. Since

$$\lim_{k \rightarrow \infty} E(y, m) = |\Omega| \min W,$$

it is immediate that

$$\bar{W}(x) = \min W \quad \text{and} \quad \text{supp } \nu|_{\Omega} \subset \{(A, \mu): W(A, \mu) = \min W\} \equiv \Sigma. \quad (3.19)$$

i.e., the support of  $\nu$  is in the energy wells, and, since we have already constructed one sequence for which the field energy tends to zero,

$$\frac{1}{2} \int_{\mathbb{R}^3} \nabla u^k (C^k)^{-1} \cdot \nabla u^k \det F^k dx \rightarrow 0, \quad (3.20)$$

whence  $u^k \rightarrow 0$  in  $V$ .

The limit deformation  $y(x)$  has gradient

$$F(x) = \int_{\mathbb{M} \times \mathbb{S}^2} A d\nu_x(A, \mu) \quad \text{in } \mathbb{R}^3 \text{ a.e. and}$$

$$F(x) = \int_{\Sigma \times \mathbb{S}^2} A \, dv_x(A, \mu) \quad \text{in } \Omega \text{ a.e.} \quad (3.21)$$

so that

$$F(x) \in \text{convex hull } \Sigma \subset D. \quad (3.22)$$

This suggests several questions. First consider any gradient Young measure  $\nu = (\nu_x)_{x \in \Omega}$  with  $\text{supp } \nu \subset \Sigma$ . Is it true that there is a sequence  $(u^k)$  with

$$\text{range } \nabla u^k \subset D \quad (3.23)$$

such that  $(\nabla u^k)$  generates  $\nu$ ? What is known is that there is such a sequence with

$$\text{range } \nabla u^k \subset t \Sigma, \quad (3.24)$$

where  $t \geq 1$  depends only on the well structure, [44]. It has also been established that if  $\Sigma$  consists of two variants, then any  $F(x)$  satisfying (3.21) may be achieved by a  $\nu$  which consists of a convex combination of 3 ([5]) or 4 ([46]) Dirac masses. The associated sequences  $(u^k)$  satisfy (3.24) with  $t = 1 + \epsilon$ , for  $\epsilon$  chosen arbitrarily small. Also in some interesting cases of self-accomodation, (3.23) may be shown to hold, Bhattacharya [7]. A general open question is whether any function  $y$  whose gradient satisfies (3.21) is a limit of finite rank laminates with support in  $D$ .

Let us now consider briefly the magnetostatic energy. In the limit, this term vanishes according to (3.20). It follows that

$$\begin{aligned} m^k F^{k-T} &\rightarrow \alpha \quad \text{in } L^\infty(\mathbb{R}^3; \mathbb{R}^3) \text{ weak}^*, \quad \alpha = 0 \text{ for } x \notin \Omega, \text{ and} \\ \text{div } (m^k F^{k-T}) &\rightarrow 0 \quad \text{in } H_{\text{loc}}^{-1}(\mathbb{R}^3). \end{aligned} \quad (3.25)$$

Thus

$$\text{div } \alpha = 0 \quad \text{in } H^{-1}(\mathbb{R}^3). \quad (3.26)$$

It need not be true in general that  $\alpha = 0$ . We briefly inquire about the relationship between  $\alpha$  and

$$\bar{m} = \int_{\Sigma \times \mathbb{S}^2} \mu \, dv_x(A, \mu) .$$

To a product of the form

$$\beta \nabla y^T = (\beta \cdot \nabla y_1, \beta \cdot \nabla y_2, \beta \cdot \nabla y_3)$$

we may seek to apply the div-curl lemma [68] provided  $\beta$  is the limit of quantities  $\beta^k$  with  $\text{div } \beta^k$  compact in  $H^{-1}$ . In our situation,  $\beta^k = m^k F^{k-T}$  satisfies this condition, (3.25), so

$$\beta^k \cdot \nabla y_i^k \rightarrow \alpha \cdot \nabla y_i \text{ in } D'.$$

Since  $(m^k F^{k-T})$  and  $(\nabla y^k)$  are bounded,

$$\bar{m} = \alpha F^T \text{ or } \alpha = \bar{m} F^{-T}. \quad (3.27)$$

We shall use this relation in the next section to illustrate the necessity of magnetic fine structure in certain configurations.

#### 4. Description of the equilibrium microstructure

The magnetostrictive material  $\text{Tb}_x\text{Dy}_{1-x}\text{Fe}_2$ ,  $x \approx .27$ , in equilibrium exhibits a herringbone configuration, with two sets of lamellar fine structures separated by a (111) plane<sup>2</sup>, cf. Figure 1. We shall focus attention on a single set of lamellae, eg., that below the indicated plane of separation in the region labelled  $\Omega^-$ . Ignoring dependence on temperature, as usual, we assume that  $W(F, m)$  is invariant under the group  $\mathbb{P}$ , the cubic group of order 24. As we have noted

$$\mathbb{P} = \{ P \in \text{SO}(3): P = (p_{ij}), p_{ij} = \pm 1 \text{ or } 0 \}. \quad (4.1)$$

We choose the pair  $(U_1, m_1)$  with

$$U_1 = 1 + \varepsilon m_1 \otimes m_1, \quad m_1 = \frac{1}{\sqrt{3}}(1, 1, 1), \quad |\varepsilon| \text{ small}. \quad (4.2)$$

---

<sup>2</sup> Crystallographic directions are referred to the putative high temperature cubic configuration.

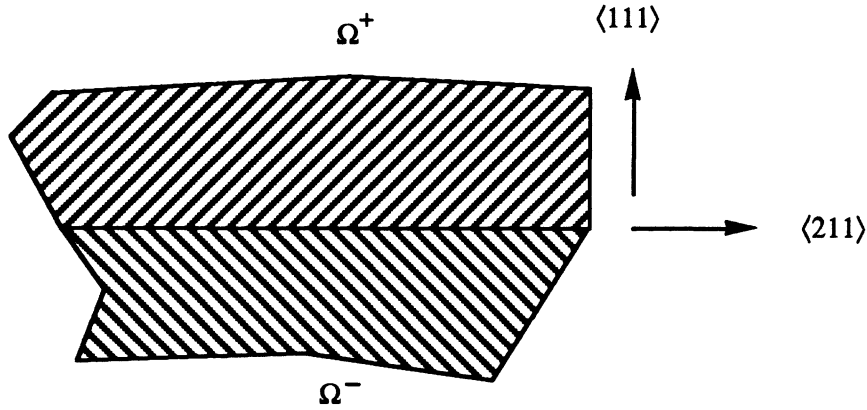


Figure 1 Schematic diagram of microstructure in TbDyFe<sub>2</sub>, illustrating herringbone structure of two sets of laminar fine structures. Crystallographic directions are indicated.

Here we have made a special choice of reference configuration (see [41] for details.) Thus the low temperature phase derives from the high temperature phase by a stretch or contraction along a principal diagonal. One may easily calculate that there are eight potential wells. With

$$m_2 = \frac{1}{\sqrt{3}}(1, -1, -1), \quad m_3 = \frac{1}{\sqrt{3}}(1, -1, 1), \quad m_4 = \frac{1}{\sqrt{3}}(-1, -1, 1), \quad (4.3)$$

these are given by the SO(3) orbits of

$$(U_i, m_i) \text{ and } (U_i, -m_i), \quad U_i = 1 + \epsilon m_i \otimes m_i, \quad i = 1, \dots, 4, \quad (4.4)$$

according to (2.17). The conclusion of Theorem 3.1 obviously holds in this situation. We now consider the variant structure, for which we prove a special case of [4], Theorem 7. To understand the statement of this theorem, we recall a few terms. Two orbits  $SO(3)M_1$  and  $SO(3)M_2$  are *mechanically compatible*, or simply, *compatible*, provided there is at least one matrix  $F_1 \in SO(3)M_1$  and one matrix  $F_2 \in SO(3)M_2$  such that  $F_2 - F_1$  is rank one. If  $F_2 - F_1 = a \otimes n$ , then there is a continuous piecewise affine deformation  $y(x)$  such that

$$\nabla y(x) = \begin{cases} F_1 & n \cdot x < \gamma \\ F_2 & n \cdot x > \gamma \end{cases}, \text{ for any given } \gamma.$$

In fact, if for one  $F_1$  there is one  $F_2$ , there are two such  $F_2$ 's and this property holds for every  $F_1 \in SO(3)M_1$ . The pairs  $(F_1, m_1)$  and  $(F_2, m_2)$  are *mechanically and magnetically compatible* provided that  $F_2 - F_1 = a \otimes n$ , as before, and

$$(m_2 F_2^{-T} - m_1 F_1^{-T}) \cdot n = 0.$$

This means that the vector field

$$\alpha(x) = \begin{cases} m_1 F_1^{-T} & n \cdot x < \gamma \\ m_2 F_2^{-T} & n \cdot x > \gamma \end{cases},$$

satisfies

$$\operatorname{div} \alpha = 0 \text{ in } H^{-1}(\mathbb{R}^3),$$

and, does not induce any field energy in the functional  $E$ , and is a first step toward constructing a minimizing sequence. The compatibility of the minimum energy wells of  $W$  is assured by the result below, cf. [41].

**THEOREM 4.1**      *Suppose that*

$$U_1 = 1 + \varepsilon m_1 \otimes m_1 \text{ and } U_2 = 1 + \varepsilon m_2 \otimes m_2, \quad (4.5)$$

*$|m_i| = 1$  and  $m_1, m_2$  independent.*

*Then*

*$SO(3)U_1$  and  $SO(3)U_2$  are compatible wells.*

*There are rotations  $R^\pm$  with axis  $p = m_1 \wedge m_2$  such that*

$$U_1 = R^\pm U_2 (1 + a^\pm \otimes n^\pm), \quad (4.6)$$

*with  $n^+ \parallel p \wedge (m_1 - m_2)$ ,  $n^- \parallel p \wedge (m_1 + m_2)$ , and  $a^\pm \cdot n^\pm = 0$ .*

*The pairs*

$$\{(U_1, m_1), (R^\pm U_2, \pm m_2 (R^\pm)^T)\}$$

*are mechanically and magnetically compatible across planes  $n^\pm \cdot x = \gamma$ .*

For example, with  $m_1$  and  $m_2$  given above,  $n^+ = \langle 100 \rangle$  and  $n^- = \langle 011 \rangle$ , in agreement with the data of D. Lord. The Theorem applies to other transitions as well;  $m_i$  could be  $\langle 100 \rangle$  or  $\langle 110 \rangle$  directions and the result specifies the twin planes for more common cubic/tetragonal, etc., transitions.

We now exhibit a minimizing sequence which has Young measure

$$v_x = \frac{1}{2}(1-\lambda)(\delta_{(U_1, m_1)} + \delta_{(U_1, -m_1)}) + \frac{1}{2}\lambda(\delta_{(R^+U_2, m_2(R^+)T)} + \delta_{(R^+U_2, -m_2(R^+)T)}), \quad x \in \Omega^-. \quad (4.7)$$

where  $0 \leq \lambda \leq 1$ . For convenience of notation, denote by  $\Omega \subset \mathbb{R}^3$  be the region occupied by the material, instead of  $\Omega^-$ , and suppose it has a sufficiently regular boundary. Set  $n = n^+$  and  $R = R^+$  and define the functions

$$\vartheta(t) = \begin{cases} -1 & 0 \leq t < \frac{1}{2} \\ +1 & \frac{1}{2} \leq t < 1 \end{cases}, \text{ and}$$

$$\eta(t) = \begin{cases} 1 & 0 \leq t < \lambda \\ 0 & \lambda \leq t < 1 \end{cases}.$$

and extend  $\vartheta$  and  $\eta$  to be periodic of period 1 on  $\mathbb{R}$ . Define  $y^k(x)$  by  $y^k(0) = 0$  and

$$\nabla y^k = F^k = (1 - \eta(kx \cdot n))U_1 + \eta(kx \cdot n)RU_2, \quad x \in \mathbb{R}^3. \quad (4.9)$$

Now in each layer where  $F^k = U_1$ , say,  $j + \lambda \leq kx \cdot n \leq j + 1$ , define

$$m^k(x) = \vartheta(kp \cdot x)m_1,$$

and in each layer where  $F^k = RU_2$ , define

$$m^k(x) = \vartheta(kp \cdot x)m_2R^T.$$

Hence,

$$m^k(x) = \vartheta(kp \cdot x)((1 - \eta(kx \cdot n))m_1 + \eta(kx \cdot n)m_2), \quad x \in \mathbb{R}^3. \quad (4.10)$$

According to this construction,

$$f^k(x) = m^k(x) F^k(x)^{-T} = \frac{\vartheta(kp \cdot x)}{1 + \varepsilon}((1 - \eta(kx \cdot n))m_1 + \eta(kx \cdot n)m_2), \quad x \in \mathbb{R}^3, \quad (4.11)$$

satisfies

$$\operatorname{div} f^k = 0 \quad \text{in } H^{-1}(\mathbb{R}^3) \quad \text{and} \quad f^k \rightarrow 0 \quad \text{in } L^\infty(\mathbb{R}^3) \text{ weak*}.$$

Hence by Lemma 3.2,

$$\operatorname{div} \chi_\Omega f^k \rightarrow 0 \quad \text{in } H^{-1}(\mathbb{R}^3).$$

Since  $W(F^k, m^k) = \min W$ , we have that for this sequence  $(y^k, m^k)$ ,

$$\lim_{k \rightarrow \infty} E(y^k, m^k) = |\Omega| \min W.$$

It is not necessary to be so precise in the construction of the minimizing sequence. It is possible to have a "slow" deformation variable and a "fast" magnetization variable, for example, and to exploit Lemma 3.2 in such a way that the magnetic compatibility across planes  $x \cdot n = \text{const.}$  is not used.

## 5. Magnetic fine structure

Using (3.27), we can investigate the magnetization distribution associated with specific mechanical microstructures. We give two illustrations of this. We shall show that (4.7) is the unique Young measure whose underlying deformation gradient is the constant matrix

$$F = (1 - \lambda)U_1 + \lambda RU_2 \quad \text{in } \Omega, \quad (5.1)$$

where  $R = R^+$  and whose support is given by (5.3) below. Consequently, any equilibrium configuration of the form described by  $\Omega^-$  in Figure 1 necessarily has magnetic fine structure. We then extend this to the composite  $\Omega^+ \cup \Omega^-$ . Indeed, in both cases our objective is to show that

$$\bar{m} = 0 \quad \text{in } \Omega. \quad (5.2)$$

Let us assume that  $\nu = (\nu_x)_{x \in \Omega}$  is a Young measure generated by a minimizing sequence  $(y^k, m^k)$  of the functional  $E$  with the properties

$$\text{supp } \nu \subset X = \{(A, \mu): A = QU_i, \mu = m_i Q^T, Q \in SO(3), i = 1, 2\} \quad (5.3)$$

where

$$U_i = 1 + \varepsilon m_i \otimes m_i, |m_i| = 1, i = 1, 2, \text{ with } m_1, m_2 \text{ independent.} \quad (5.4)$$

We further assume that the underlying deformation gradient is given by (5.1) in a neighborhood  $\Omega$ . In addition, we assume that  $|\varepsilon|$  is small. First of all, it is known ([5],[46]) and easily shown that under the conditions of (4.8), (4.9) the deformation portion of the Young measure whose support is given by (5.3) is unique and given by a convex combination of Dirac masses. Hence in view of the restriction on the support of  $\nu$  given by (5.3),

$$\nu_x = (1 - \lambda) \{ (1 - \gamma_1(x)) \delta_{U_1} \otimes \delta_{m_1} + \gamma_1(x) \delta_{U_1} \otimes \delta_{-m_1} \} +$$

$$\lambda\{(1 - \gamma_2(x)) \delta_{RU_2} \otimes \delta_{m_2 R^T} + \gamma_2(x) \delta_{RU_2} \otimes \delta_{-m_2 R^T}\}, \quad (5.5)$$

where  $0 \leq \gamma_i(x) \leq 1$ . Now

$$\bar{m}(x) = \int_{\mathcal{X}} \mu \, dv_x(A, \mu) \quad \text{in } \Omega \text{ a.e. and} \quad (5.6)$$

$$\alpha(x) = \int_{\mathcal{X}} \mu A^{-T} \, dv_x(A, \mu) \quad \text{in } \Omega \text{ a.e..} \quad (5.7)$$

Thus

$$\bar{m} = ((1 - \lambda)(1 - 2\gamma_1)m_1 + \lambda(1 - 2\gamma_2)m_2 R^T) \chi_\Omega \quad (5.8)$$

while on the other hand

$$\begin{aligned} \alpha &= (1 - \lambda)\{(1 - \gamma_1) m_1 U_1^{-T} - \gamma_1 m_1 U_1^{-T}\} \chi_\Omega + \\ &\quad \lambda\{(1 - \gamma_2) m_2 R^T (RU_2)^{-T} - \gamma_2 m_2 R^T (RU_2)^{-T}\} \chi_\Omega \end{aligned}$$

Since  $U_i^{-T} = U_i^{-1}$ , the above simplifies to

$$\alpha = \{(1 - \lambda)(1 - 2\gamma_1) m_1 U_1^{-1} + \lambda(1 - 2\gamma_2) m_2 U_2^{-1}\} \chi_\Omega \quad (5.9)$$

We now seek to identify the quantities in the expression  $\bar{m} = \alpha F^T$ , cf. (3.27). Setting  $\beta_i = (1 - 2\gamma_i)$ ,

$$\alpha F^T = \{(1 - \lambda)\beta_1 m_1 U_1^{-1} + \lambda\beta_2 m_2 U_2^{-1}\} \{(1 - \lambda)U_1 + \lambda U_2 R^T\} \quad \text{in } \Omega.$$

Since this expression must equal (5.9),

$$\lambda(1 - \lambda)\{\beta_1 m_1 (1 - U_1^{-1} U_2 R^T) + \beta_2 m_2 (R^T - U_2^{-1} U_1)\} = 0. \quad (5.10)$$

The only case of interest is  $0 < \lambda < 1$ . If the two (constant) vectors

$$q_1 = m_1 (1 - U_1^{-1} U_2 R^T) \quad \text{and} \quad q_2 = m_2 (R^T - U_2^{-1} U_1) \quad (5.11)$$

are independent, then  $\beta_1 = \beta_2 = 0$ . If they are dependent, then the functions  $\beta_i(x)$  are proportional: there is a scalar  $c \in \mathbb{R}$  for which



$$\beta_2(x) = c \beta_1(x) \quad \text{or} \quad \beta_1(x) = 0 \quad \text{in } \Omega, \quad (5.12)$$

Hence, since  $m_i U_i^{-1} = \frac{1}{1+\varepsilon} m_i$ ,

$$\alpha = \frac{\beta_1}{1+\varepsilon} ((1-\lambda)m_1 + \lambda c m_2) \chi_\Omega. \quad (5.13)$$

Suppose at this point that (5.1) is satisfied in the entire region occupied by the material,  $\Omega$ . Thus  $\alpha$  has constant direction and satisfies

$$\operatorname{div} \alpha = 0 \quad \text{in } H^{-1}(\mathbb{R}^3).$$

This implies that  $\alpha = 0$ . In fact any mapping of the form

$$\zeta \rightarrow \int_{\mathbb{R}^3} f \nabla \zeta \, dx$$

where  $f \in L^2(\mathbb{R}^3)$  has compact support either has full rank or  $f$  vanishes identically, cf. [40] Lemma 4.1. By (5.13),

$$\int_{\mathbb{R}^3} \frac{\beta_1}{1+\varepsilon} \chi_\Omega \nabla \zeta \, dx \cdot ((1-\lambda)m_1 + \lambda c m_2) = 0,$$

so

$$f = \frac{\beta_1(x)}{1+\varepsilon} = 0.$$

Consequently,  $\beta_1 = \beta_2 = 0$  which implies that  $\gamma_1 = \gamma_2 = \frac{1}{2}$ . This verifies (5.2).

In fact,  $q_1$  and  $q_2$  of (5.11) are always dependent. Manipulation of equation (5.10) reveals that it is equivalent to

$$(\beta_1 m_1 U_1^{-1} - \beta_2 m_2 U_2^{-1})(U_1 - U_2 R^T) = 0,$$

or

$$\frac{1}{1+\varepsilon} (\beta_1 m_1 - \beta_2 m_2)(U_1 - U_2 R^T) = 0. \quad (5.14)$$

Now

$$U_1 - U_2 R^T = n \otimes R U_2 a$$

is a rank one matrix. Since  $m_1$  and  $m_2$  are independent, it is always possible to find  $\beta_1$  such that (5.14) holds. In fact, some additional algebra shows that  $\beta_1 + \beta_2 = 0$ .

Let us now consider the composite material described in Figure 1, assuming that the variant proportion is constant in the top and the bottom. An expression for the deformation identical to (5.1) holds in each of  $\Omega^+$  and  $\Omega^-$ . We find by the preceding reasoning that  $\alpha$  has constant direction in each of  $\Omega^-$  and  $\Omega^+$ . Arguing in a manner similar to the single laminate case, we conclude again that  $\alpha = 0$ .

## References

- [1] Anzellotti, G., Baldo, S., and Visintin, A. 1991 Asymptotic behavior of the Landau-Lifshitz model of ferromagnetism, *Applied Mathematics and Optimization*, 23, 171-192
- [2] Ball, J. M. 1981 Global invertibility of Sobolev functions and the interpenetration of matter, *Proc. R. Soc. Edin.* 88A, 315-328
- [3] Ball, J. M. 1989 A version of the fundamental theorem for Young measures, *PDE's and continuum models of phase transitions*, Lecture Notes in Physics, 344, (Rascle, M., Serre, D., and Slemrod, M., eds.) Springer, 207-215
- [4] Ball, J. M. and James, R. 1987 Fine phase mixtures as minimizers of energy, *Arch. Rat. Mech. Anal.*, 100, 15-52
- [5] Ball, J. M. and James, R. 1991 Proposed experimental tests of a theory of fine microstructure and the two well problem, *Phil. Trans. Roy. Soc. Lond.* (to appear)
- [6] Ball, J. M. and Zhang, K. 1990 Lower semicontinuity of multiple integrals and the biting lemma, *Proc. Royal Soc. Edinburgh*, 114A, 367-379
- [7] Battacharya, K. Self accommodation in martensite, *Arch. Rat. Mech. Anal.* (to appear)
- [8] Battacharya, K. Wedge-like microstructure in martensite, (to appear)
- [9] Brandon, D. and Rogers, R. The coercivity paradox and nonlocal ferromagnetism, (to appear)
- [10] Brown, W.F. 1962 *Magnetostatic Principles in Ferromagnetism*, Vol. 1 of Selected Topics in Solid State Physics (ed. E.P. Wohlfarth), North-Holland.
- [11] Brown, W.F. 1963 *Micromagnetics*, John Wiley and Sons, New York.
- [12] Brown, W.F. 1966 *Magnetoelastic Interactions*, Vol. 9 of Springer Tracts in Natural Philosophy (ed. C. Truesdell), Springer-Verlag.
- [13] Chipot, M. and Kinderlehrer, D. 1988 Equilibrium configurations of crystals, *Arch. Rat. Mech. Anal.* 103, 237-277
- [14] Chipot, M. Numerical analysis of oscillations in nonconvex problems, (to appear)
- [15] Ciarlet, P. and Necas, J. 1987 Injectivity and self contact in nonlinear elasticity, *Arch. Rat. Mech. Anal.*, 19, 171-188
- [16] Clark, A. E. 1980 Magnetostrictive rare earth - Fe<sub>2</sub> compounds, *Ferromagnetic Materials, Vol 1* (Wohlfarth, E. P. ed) North Holland, 532 - 589
- [17] Collins, C. and Luskin, M. 1989 The computation of the austenitic-martensitic phase transition, *Lecture Notes in Physics 344* (ed. M. Rascle, D. Serre and M. Slemrod), Springer-Verlag, 34-50.
- [18] Collins, C. and Luskin, M. Numerical modeling of the microstructure of crystals with symmetry-related variants, *Proc. ARO US-Japan Workshop on Smart/Intelligent Materials and Systems*, Technomic
- [19] Collins, C. and Luskin, M. Optimal order error estimates for the finite element approximation of the solution of a nonconvex variational problem, to appear
- [20] Collins, C., Kinderlehrer, D., and Luskin, M. Numerical approximation of the solution of a variational problem with a double well potential, *SIAM J. Numer. Anal.*
- [21] Craik, D.J. and Tebble, R. S. 1965 *Ferromagnetism and Ferromagnetic Domains*, North-Holland.
- [22] Dacorogna, B. 1989 *Direct methods in the Calculus of Variations*, Springer
- [23] Ericksen, J. L. 1979 On the symmetry of deformable crystals, *Arch. Rat. Mech. Anal.* 72, 1-13
- [24] Ericksen, J. L. 1980 Some phase transitions in crystals, *Arch. Rat. Mech. Anal.* 73, 99-124
- [25] Ericksen, J. L. 1981 Changes in symmetry in elastic crystals, *IUTAM Symp. Finite Elasticity* (Carlson, D.E. and Shield R.T., eds.) M. Nijhoff, 167-177
- [26] Ericksen, J. L. 1982 Crystal lattices and sublattices, *Rend. Sem. Mat. Padova*, 68, 1-9

- [27] Ericksen, J. L. 1984 The Cauchy and Born hypotheses for crystals, *Phase Transformations and Material Instabilities in Solids*, (Gurtin, M., ed) Academic Press, 61-78
- [28] Ericksen, J. L. 1986 Constitutive theory for some constrained elastic crystals, *Int. J. Solids Structures*, 22, 951 - 964
- [29] Ericksen, J. L. 1987 Twinning of crystals I, *Metastability and Incompletely Posed Problems*, IMA Vol. Math. Appl. 3, (Antman, S., Ericksen, J.L., Kinderlehrer, D., Müller, I., eds) Springer, 77-96
- [30] Ericksen, J. L. 1988 Some constrained elastic crystals, *Material Instabilities in Continuum Mechanics*, (Ball, J. ed.) Oxford, 119 - 136
- [31] Ericksen, J. L. 1989 Weak martensitic transformations in Bravais lattices, *Arch. Rat. Mech. Anal.*, 107, 23 - 36
- [32] Firooze, N. and Kohn, R. 1991 Geometric parameters and the relaxation of multiwell energies, IMA preprint Series 765
- [33] Fonseca, I. 1988 The lower quasicontinuous envelope of the stored energy function for an elastic crystal, *J. Math. pures et appl.*, 67, 175-195
- [34] Fonseca, I. Lower semicontinuity of surface measures (to appear)
- [35] Fonseca, I. The Wulff Theorem revisited (to appear)
- [36] James, R. D. 1988 Microstructure and weak convergence, *Proc. Symp. Material Instabilities in Continuum Mechanics*, Heriot-Watt, (Ball, J. M., ed.), Oxford, 175-196
- [37] James, R. D. 1989 Relation between microscopic and macroscopic properties of crystals undergoing phase transformation, in *Proc. 7th Army Conf. on Applied Mathematics and Computing* (ed. F. Dressel).
- [38] James, R. D. and Kinderlehrer, D. 1989 Theory of diffusionless phase transitions, *PDE's and continuum models of phase transitions*, Lecture Notes in Physics, 344, (Rascle, M., Serre, D., and Slemrod, M., eds.) Springer, 51-84
- [39] James, R. D. and Kinderlehrer, D. 1990 An example of frustration in a ferromagnetic material, *Nematics: Mathematical and Physical Aspects*, (Coron, J.-M., Ghidaglia, J.-M., and Hélein, F., eds), Kluwer NATO ASI series, 201-222
- [40] James, R. D. and Kinderlehrer, D. 1990 Frustration in ferromagnetic materials, *Cont. Mech. Therm.* 2, 215-239
- [41] James, R. D. and Kinderlehrer, D. A theory of magnetostriction with application to TbDyFe<sub>2</sub> (to appear)
- [42] James, R.D. and Müller, S. to appear
- [43] Kinderlehrer, D. 1988 Remarks about the equilibrium configurations of crystals, *Proc. Symp. Material instabilities in continuum mechanics*, Heriot-Watt (Ball, J. M. ed.) Oxford, 217-242
- [44] Kinderlehrer, D. and Pedregal, P. Characterizations of Young measures generated by gradients, *Arch. Rat. Mech. Anal.* (to appear)
- [45] Kinderlehrer, D. and Pedregal, P. Caractérisation des mesures de Young associées à un gradient, C.R.A.S. Paris (to appear)
- [46] Kinderlehrer, D. and Pedregal, P. Remarks about Young measures supported on two wells (to appear)
- [47] Kléman, M. 1983 *Points, Lines and Walls*, John Wiley and Sons, New York.
- [48] Kohn, R. V. 1991 The relaxation of a double-well energy, *Cont. Mech. Therm.*, 3, 193-236
- [49] Kohn, R.V. 1989 The relationship between linear and nonlinear variational models of coherent phase transitions, in *Proc. 7th Army Conf. on Applied Mathematics and Computing* (ed. F. Dressel).
- [50] Landau, L.D. and Lifshitz, E. M. 1935 *Physik. Z. Sowjetunion* 8, 337-346.
- [51] Landau, L.D., Lifshitz, E. M., and Pitaevskii, L. P. 1984 *Electrodynamics of continuous media*, Vol. 8 of Course of Theoretical Physics, Pergamon Press.
- [52] Lifshitz, E.M. 1944 On the magnetic structure of iron, *J. Physics* 8, 337-346.
- [53] Lord, D. 1990 Magnetic domain observations in TbDyFe<sub>2</sub>, IMA lecture
- [54] Luskin, M. and Ma, L. 1990 Analysis of the finite element approximation of microstructure in micromagnetics, UMSI report 90/164
- [55] Ma, L. to appear
- [56] Marcellini, P. 1985 Approximation of quasicontinuous functions and lower semicontinuity of certain quasicontinuous integrals, *Manu. Math.*, 51, 1-28
- [57] Matos, J. The absence of fine microstructure in  $\alpha$ - $\beta$  quartz, (to appear)
- [58] Pedregal, P. 1989 Thesis, University of Minnesota
- [59] Pedregal, P. 1989 Weak continuity and weak lower semicontinuity for some compensation operators, *Proc. Royal Soc. Edin.* 113, 267 - 279



- [60] Rogers, R.C. 1988 Nonlocal variational problems in nonlinear electromagneto-elastostatics, *SIAM J. Math. Anal.* 19, 1329-1347.
- [61] Rogers, R.C. 1990 A nonlocal model for the exchange energy uin ferromagnetic materials, *J. Int. Eqns. Appl.* (to appear)
- [62] Sethna, J. 1987 Theory of the blue phases of chiral nematic liquid crystals, in *Theory and Applications of Liquid Crystals* (ed. J.L. Ericksen and D. Kinderlehrer), IMA Vol. Math. Appl. 5, Springer, 305-324
- [63] Stoner, E.C. 1945 The demagnetizing factors for ellipsoids, *Phil. Mag.* 36, 803-821.
- [64] Sverak, V. 1991 Quasiconvex functions with subquadratic growth, *Proc. R. Soc. Lond.*, 433, 723-725
- [65] Sverak, V. On Tartar's conjecture (to appear)
- [66] Sverak, V. On the problem of two wells, (to appear)
- [67] Sverak, V. On the regularity of the Monge-Ampère equation without convexity, (to appear)
- [68] Tartar, L. 1979 Compensated compactness and applications to partial differential equations, *Nonlinear analysis and mechanics: Heriot Watt Symposium, Vol I V*(Knops, R., ed.) Pitman Res. Notes in Math. 39, 136-212
- [69] Tartar, L. 1983 The compensated compactness method applied to systems of conservation laws, *Systems of nonlinear partial differential equations* (Ball, J. M., ed) Riedel
- [70] Toupin, R. 1956 The elastic dielectric, *J. Rat. Mech. Anal.*, 5, 849 - 915
- [71] Visintin, A. 1985 On Landau-Lifshitz equations in ferromagnetism, *Japan. J. Appl. Math.*, 2, 69-84
- [72] Young, L. C. 1969 *Lectures on calculus of variations and optimal control theory*, W.B. Saunders
- [73] Zhang, K. A construction of quasiconvex functions with linear growth at infinity (to appear)
- [74] Zhang, K. Rank-one connections and the three "well" problem, (to appear)

R.D. James  
 Department of Aerospace  
 Engineering and Mechanics  
 University of Minnesota  
 Minneapolis, MN 55455

D. Kinderlehrer  
 Department of Mathematics and  
 Center for Nonlinear Analysis  
 Carnegie Mellon University  
 Pittsburgh, PA 15213-3890